

Wieland-M05

CuZn5
C21000

Rolled Products

Material Designation	
EN	CuZn5
UNS*	C21000

* Unified Numbering System (USA)

Chemical Composition (Reference)	
Cu	95 %
Zn	balance

Typical Applications
• Jewellery and metal goods
• Components for the electrical industry

Physical Properties*		
Electrical Conductivity	MS/m %IACS	33 57
Thermal Conductivity	W/(m·K)	243
Coefficient of Electrical Resistance**	10 ⁻³ /K	2.6
Coefficient of Thermal Expansion**	10 ⁻⁶ /K	18.0
Density	g/cm ³	8.86
Modulus of Elasticity	GPa	127
Specific Heat	J/(g·K)	0.380
Poisson's Ratio		0.34

* Reference values at room temperature

** Between 0 and 300 °C


Fabrication Properties	
Capacity for Being Cold Worked	excellent
Machinability	less suitable
Capacity for Being Electroplated	excellent
Capacity for Being Hot-Dip Tinned	excellent
Soft Soldering	excellent
Resistance Welding	good
Gas Shielded Arc Welding	good
Laser Welding	fair

Corrosion Resistance
Wieland-M05 has a very low sensitivity to stress corrosion cracking. The material is largely resistant to industrial atmosphere but not resistant to oxidizing acids.


Mechanical Properties				
Temper		R230	R270	R340
Tensile Strength R _m	MPa	230–280	270–350	≥ 340
Yield Strength R _{p0.2}	MPa	≤ 130	≥ 200	≥ 280
Elongation A _{50mm}	%	≥ 36	≥ 12	≥ 4

Temper	H045	H075	H110
Hardness HV	45–75	75–110	≥ 110

Electrical Conductivity

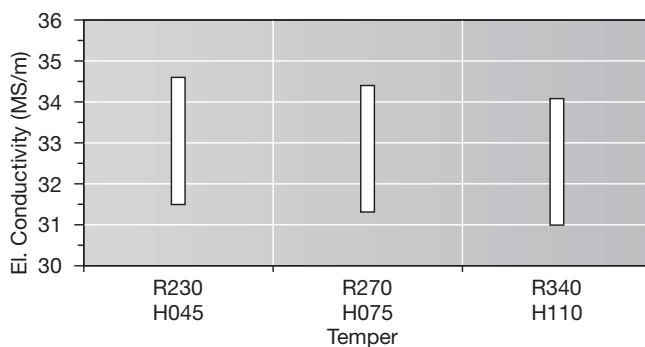


Bendability (Strip Thickness t ≤ 0.5 mm)

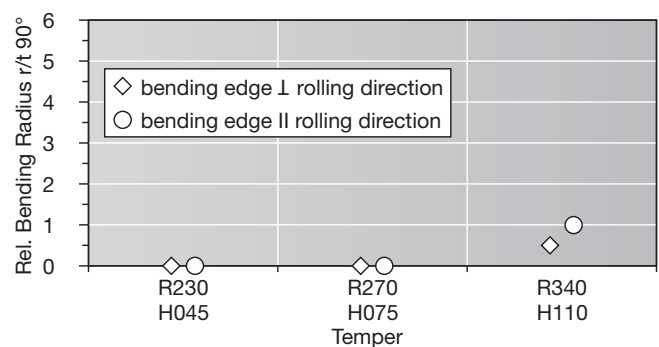

Wieland-M05

CuZn5
C21000

Resistance to Softening

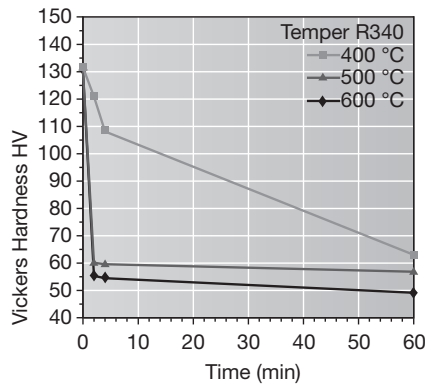

Vickers hardness
after heat treatment
(typical values)

Fatigue Strength

The fatigue strength is defined as the maximum bending stress amplitude which a material withstands for 10^7 load cycles under symmetrical alternate load without breaking. It is dependent on the temper tested and is about $\frac{1}{3}$ of the tensile strength R_m .

Types and Formats Available

- Standard coils with outside diameters up to 1400 mm
- Traverse-wound coils with drum weights up to 1.5 t
- Multicoil up to 5 t
- Hot-dip tinned strip
- Contour-milled strip

Dimensions Available

- Strip thickness from 0.10 mm, thinner gauges on request
- Strip width from 3 mm, however min. 10 x strip thickness

Wieland-Werke AG

www.wieland.com

Rolled Products Division

Graf-Arco-Str. 36, 89079 Ulm, Germany, Phone +49 (0)731 944-0, Fax +49 (0)731 944-2772, info@wieland.de
Ziegeleiweg 20, 42555 Velbert-Langenberg, Germany, Phone +49 (0)731 944-0, Fax +49 (0)731 944-9270, info@wieland.de
Lantwattenstr. 11, 78007 Villingen-Schwenningen, Germany, Phone +49 (0)731 944-0, Fax +49 (0)731 944-7108, info@wieland.de

This leaflet is for your general information only and is not subject to revision. No claims can be derived from it unless there is evidence of intent or gross negligence. The data given are no warranty that the product is of a specified quality and they cannot replace expert advice or the customer's own tests.